

5-15-2020

## **A novel approach for using silica nanoparticles in a proppant pack to fixate coal fines**

Faisal Ur Rahman Awan  
*Edith Cowan University*

Alireza Keshavarz  
*Edith Cowan University*

Hamed Akhondzadeh  
*Edith Cowan University*

Sarmad Al-Anssari  
*Edith Cowan University*

Stefan Iglauer  
*Edith Cowan University*

Follow this and additional works at: <https://ro.ecu.edu.au/ecuworkspost2013>



Part of the [Engineering Commons](#)

---

[10.1071/AJ19031](https://doi.org/10.1071/AJ19031)

This is an Author's Accepted Manuscript of:

Awan, F. U. R., Keshavarz, A., Akhondzadeh, H., Al-Anssari, S., & Iglauer, S. (2020). A novel approach for using silica nanoparticles in a proppant pack to fixate coal fines. *The APPEA Journal*, 60(1), 88-96.

<https://doi.org/10.1071/AJ19031>

This Journal Article is posted at Research Online.

<https://ro.ecu.edu.au/ecuworkspost2013/8169>

# **A Novel Approach for Using Silica Nanoparticles in a Proppant Pack to Fixate Coal Fines**

Faisal Ur Rahman Awan<sup>A, B, D</sup>

Alireza Keshavarz<sup>A</sup>

Hamed Akhonzadeh<sup>A</sup>

Sarmad Al-Anssari<sup>A, C</sup>

Stefan Iglauer<sup>A</sup>

<sup>A</sup> School of Engineering, Edith Cowan University, Joondalup, 6027, Western Australia, Australia

<sup>B</sup> Department of Petroleum and Gas Engineering, Dawood University of Engineering and Technology, Karachi, 74800, Sindh, Pakistan

<sup>C</sup> Department of Chemical Engineering, University of Baghdad, Baghdad 10071, Iraq

<sup>D</sup> Corresponding author. e-Mail: f.awan@ecu.edu.au

## **Abstract**

Hydraulic fracturing operations in coal seam gas (CSG) reservoirs are highly prone to release coal fines. Coal fines inevitably cause mechanical pump failure and permeability damage as a result of their hydrophobicity, aggregation in the system, and pore-throat blockage. Thus, one approach to affix these coal fines at their source, and to retard generation, is to introduce a nanoparticle-treated-proppant pack. Thus, this research explores coal fines retention (known as adsorption) in a proppant pack using nanoparticles. In the study, the electrolytic environment, pH, flow rate, temperature, and pressure were kept constant, while the variables were concentration of silica nanoparticles (0 – 0.1 wt%) and coal fines concentration (0.1 – 1 wt%). The objective was to identify silica nano-formulations that fixate coal fine dispersions effectively. Subsequently, the coal suspensions flowed through a glass bead proppant pack treated with and without nanoparticles, and then analyzed via a particle counter. The quantitative results from particle counter analysis showed that the proppant pack with nanoparticle treatment strongly affects the fixation ability of coal fines. The proppant pack without nanoparticle treatment showed up to 30% adsorption and flowed through the proppant untreated, whilst proppant pack treated with nanoparticles showed up to 74% adsorption; hence, more exceptional affixation ability to the coal fines. Further, the results indicated that the zeta potential of silica nanoparticles at higher salinity becomes unstable, i.e., ~ -20 mV; this low value helps the proppant pack treated with nanoparticles to attach coal fines to it. The ability of nanoparticles to adsorb coal fines is due to its highly active surface, and high specific surface area.

## **Keywords**

Coal fines, nanoparticles, nanofluid, fines fixation, CBM, Proppant pack

## 1. Introduction

The application of nanoparticles has proven to be beneficial in the upstream oil and gas industry (Yang *et al.* 2015). Several applications like water flood displacement (Yuan and Moghanloo 2018; Bahraminejad *et al.* 2019; Najimi *et al.* 2019), fines fixation (Huang *et al.* 2010b; Assef *et al.* 2014; Yuan 2017; Zheng *et al.* 2018), and enhanced oil recovery (Yousefvand and Jafari 2015; Bera and Belhaj 2016; Yuan and Wood 2018; Asl *et al.* 2020) have been studied and experimented upon in this capacity. The use of nanoparticles to control fines release and fix them at or near the source of their origin has been studied comprehensively in both sandstones (Kia *et al.* 1987; Mohan and Fogler 1997; Rozo *et al.* 2007; Zeinijahromi *et al.* 2012; Bin *et al.* 2016; Hasannejada *et al.* 2017) and carbonates (Qajar *et al.* 2013; Al-Anssari *et al.* 2016; Al-Anssari *et al.* 2017b; Al-Anssari *et al.* 2018). The behavior of Coal Bed Methane (CBM) reservoir fines with nanoparticles, which are considerably different from sandstone fines, has yet to be comprehensively explored.

Compared to conventional reservoirs, CBM reservoirs are relatively weaker and are likely to fail in all operating stages of well development, especially while drilled in horizontal or high-angle directed trajectories (Palmer *et al.* 2005). CBM reservoirs have critical conditions to release fine. A critical salt concentration (CSC) exists in porous media (Khilar and Fogler 1984; Blume *et al.* 2005) below which fines can detach from the rock matrix. However, no presence exists of the validated agreement as to CSC in fractured media. The theoretical explanation of fines detachment / attachment has been explained using the Derjaguin–Landau–Verwey–Overbeek (DLVO) theory and extended DLVO theory. The basic premise is that if the attaching force/torque is higher than the detaching (repulsive) force/torque, then the particle will dislodge from the bulk rock matrix/structure and vice versa if the detaching (repulsive) force/torque is higher than the attractive force/torque. (Lever and Dawe 1984; Sharma *et al.* 1992; Schembre and Kovscek 2005; Rosenbrand *et al.* 2015). The size of coal fines varies according to the production stage, i.e., the usual size of coal fines found during the water production stage is usually lower than the size of coal fines generated during the gas production stage. When salinity is decreased, mobile particles also decrease in the order of size. This means that larger particles are released when ionic strength is more, and when ionic strength is decreased the smaller particles are mobilized (Keshavarz *et al.* 2014). The grain size and concentration of coal fines differ during various production stages (Zhao *et al.* 2016). Generally, two size categories can be distinguished, as follows:

1. Small-sized coal fines are produced during post-completion hydraulic fracture back-flow and in the production stage.

2. Large-sized coal fines are produced during drilling and completion (Han *et al.* 2015).

Coal fines generation and migration cause a reduction in conductivity and fracture length, thereby damaging the dewatering process (Zou *et al.* 2014). The factors that affect the production of coal fines output are:

1. Engineering aspects (well type, drilling operations/technology, hydraulic fracturing, completion technology, and the CBM production system) (Zhao *et al.* 2016; Geng *et al.* 2017).

2. Geological factors (tectonic stress, rock characteristics, structural characteristics of the coal, coal strength) (Zhao *et al.* 2016).

Bituminous coal fines have been shown to cause a 35% decline in permeability when subjected to water flow (Guo *et al.* 2016) and a 24.4% decline in conductivity when subjected to only 2% of coal fines flow into the proppant pack (Zou *et al.* 2014). Thus, coal fines can block the proppant pack and cause a decline in fracture conductivity (Bai *et al.* 2017), resulting in reduced production and failure of production equipment (Marcinew and Hinkel 1990; Badalyan *et al.* 2016). Several authors have studied coal fines suspension thus far, but have largely performed experiments in DI or distilled water (Zou *et al.* 2014), while hydraulic fracturing fluid is usually saline (nearly 0.6 M) to be geo-chemically compatible with reservoir formations fluid (Guo *et al.* 2015; Patel *et al.* 2016; Shi *et al.* 2018). The zeta-potential of coal suspension in DI water has been reported as -43.34 mV for bituminous (Shi *et al.* 2018) and anthracite as -20.5 mV (Zou *et al.* 2014); however, pH has not been mentioned as a crucial factor in determining the dispersion stability via zeta-potential measurements and has not been studied accordingly.

Fixating coal fines at their source of origin may be done by:

a) using nanoparticles and modified nanoparticles that alter the surface chemistry of fines by interacting with nanoparticles (Huang *et al.* 2010a),

b) employing micro-proppants before introducing larger proppants (also known as graded proppant injection) so that the fine particles are inhibited from moving into the proppant

pack at or near its place of origin (Kumar *et al.* 2012; Keshavarz *et al.* 2014; Keshavarz *et al.* 2015; Keshavarz *et al.* 2016),

c) adding chemicals to the fracturing fluid for agglomerating fragments of coal fines and fixing them at the source (Shi *et al.* 2018). Consequently, dispersing coal fines can be completed via two modes: physical and chemical.

i. Physically, researchers have developed models for straining particles in the pore throat, where the critical value of consensus among them is of one to six ratio, also known as a one-sixth rule. This rule notes that if the reservoirs formation fines diameter (d) is six times less than its gravel pack diameter (D) i.e.  $\frac{d}{D} < \frac{1}{6}$ , the fines will not strain (Elena Rodríguez 2007; Zou *et al.* 2014).

ii. Polymeric surfactant-based chemicals injected along with fracturing fluid to disperse and move up to the surface along with well fluids (Magill *et al.* 2010); (Pan *et al.* 2015).

Thus, fines migration is one of the most crucial phenomena for formation damage in CBM, where this challenge has not been addressed comprehensively. Limited studies are available to suggest that coal fines generation could be controlled at or near the source using metal oxides nanoparticles (Huang *et al.* 2010a; Patel *et al.* 2016). This paper will provide further insights into coal fines behavior when treated with silica nanoparticles in a proppant pack. The results show that coal fines can be adsorbed effectively using silica nanoparticles (NPs). An effective concentration of 0.1 wt% of silica NPs is recommended for achieving better adsorption of fines.

## **2. Methods and Materials**

### **2.1. Materials**

Coal lumps from coal mines in Morgantown, West Virginia, USA, were retrieved with a vitrinite reflectance of 0.91, indicative of highly volatile bituminous coal (Moore 2012). Furthermore, the composition of macerals and minerals was 97.4% and 2.6%, respectively. The properties of the coal sample are displayed in Table 1. The coal lump was crushed into smaller sizes by mortar and pestle method, where the coal fines used in this study were sieved using an electric sieve shaker. Subsequently, the coal fines sieved in 0.038 mm – 0.020 mm were used for the series of the experiment of adsorption and coal fines fixation in the proppant pack column. The coal fines size range studied in this work (0.038 mm – 0.020 mm) is consistent

with previously reported studies (Huang *et al.* 2010a; Bai *et al.* 2015; Zhao *et al.* 2016; Bai *et al.* 2017).

The glass bead proppant was kindly provided by Potters beads of Metal Finishing Glass Beads Potters, with a nominal diameter (80%) Ballotini ® Metal Finishing Beads of Potter Designation B, US Sieve 30-40 (600-475 microns), and minimum roundness of 65%, where the composition of glass beads can be seen in Table 2. Using the electrical sieve shaker, proppants were sieved to US sieve size of 35 (~475 microns) that were used in the adsorption proppant pack experiments.

The silica nanoparticles are insoluble, hydrophilic, and non-polar in water, where those used in this study were procured from Sigma-Aldrich. The properties of the silica nanoparticles are presented in Table 3. An electrolyte of 0.6 M NaCl (as compared to standard saline) was used in the adsorption experiments. A constant pH of  $9.0 \pm 0.2$  was set in all of the experiments as similar to coalbed methane reservoirs. Various concentrations of silica nanoparticles were used to formulate nanofluids. DI-water (Ultrapure Type 1 Water) was used as a base fluid for the nanofluid and to formulate 0.01 M and 0.6 M brine after mixing with NaCl (58.44 g/mol, purity  $\geq 99.5$  mol%, from Rowe Scientific).

## 2.2. Methodology

Various SiO<sub>2</sub> NPs concentrations (0.01 – 0.1 wt%), based in 0.01 M and 0.6 M brine-based solutions, were investigated in various coal concentration (0.1-1 wt%) to examine their stability, adhesion to the glass beads proppant, and coal fines adsorption efficiency. The formulation of nanofluids was carried out with two constituents, the dispersed phase and the dispersion medium. The dispersed phase was nano-sized silicon dioxide (SiO<sub>2</sub>) - also known as SNPs or Silica NPs, with weight percentages ranging from 0.01 to 0.10, while the dispersion medium was DI water, 0.01 M and 0.6 M NaCl. The dispersion stability was investigated using Malvern Z3600 Nano zeta sizer. The nanofluids were formulated by sonicating nanoparticles in the base fluid (Mahdi Jafari *et al.* 2006) using an ultrasonic processor (VCX 750, a 750-watt ultrasonic processor, frequency - 20 kHz from Sonics & Materials, Inc.). Whilst the time and power of the sonication process depends mainly on a load of dispersed nanoparticles (Shen and Resasco 2009), in this work all the formulated dispersions were sonicated with the same sonication time, energy, amplitude and power of 300 seconds, 4 MJ, 30%, and 240 V respectively to assure a duplicated conditions for all formulations. The prepared nanofluids

were visually observed to assess any significant instability in the behavior of the nanoparticles during the required soaking period. All experiments were carried out under ambient conditions of pressure = 101.3 kPa and temperature of  $295.15 \pm 3$  K.

The process of adsorption of sandstone fines using nanoparticles affixed on glass beads has also been studied by Huang *et al.* (2008) and Ahmadi *et al.* (2013) in addition to other researchers (Huang *et al.* 2008b, 2008a; Belcher *et al.* 2010; Huang *et al.* 2010b; Ahmadi *et al.* 2013b, 2013a; Habibi *et al.* 2013; Habibi *et al.* 2014). However, SNPs coating onto the proppant pack quantitatively has only been discussed by a few researchers such as Abhishek and Hamouda (Abhishek and Hamouda 2017). The only reported patent of using nanoparticles for affixing coal fines highlights the use of MgO to affix coal fines (Huang *et al.* 2010a). The selection of the proppant is influenced by the mechanical properties of the formation rock and the properties of the proppant itself. The parameters that impacted the selection of the proppant include crush resistance and size of the proppant amongst others. Hollow glass spheres have been reported to have the least specific gravity of 0.8 to 1.4 in all the lightweight proppants (Parker *et al.* 2012; Liang *et al.* 2016).

The method of affixing nanoparticles onto the surface of proppants is critical to the experiments; thus, in this research, we have soaked the NPs for 24 hours and calculated the nanoparticle coating efficiency via turbidity results. Note that SDBS (an anionic surfactant) is used in all experiments to flow through the slurry with minimal adsorption. The adsorption efficiency is defined in Eq. 1 (Habibi *et al.* 2014). The results of influent and effluent slurry were obtained using the particle counter sizer.

$$\text{Adsorption efficiency (\%)} = 100 - \left[ \frac{C_{\text{eff}}}{C_{\text{in}}} \times 100 \right] \quad \text{Eq. 1}$$

Where,

$C_{\text{eff}}$ : Concentration of coal fines in the effluent slurry, gm/cc

$C_{\text{in}}$ : Concentration of coal fines in the influent slurry, gm/cc

A glass column was used in all of the experiments of adsorption, in which flow took place merely because of gravitational force, where a schematic of the procedure adopted in the column can be seen in Fig. 1 below.

### 2.3. Experimental set-up workflow

The laboratory study model and equipment will be adapted from Habibi et al. and Ahmadi al. and used to see the effect of silica nanoparticles on coal fines adsorption (Ahmadi et al. 2013b, 2013a; Habibi et al. 2013; Arab et al. 2014; Habibi et al. 2014). In this study, bare silica nanoparticles, as well as treated silica nanoparticles with Sodium Dodecyl Benzene Sulfonate (SDBS), were analyzed with a Malvern Nano Zeta Sizer to determine their stability. Following this, a turbidity calibration curve for silica NPs was made using a HACH 2000 Turbidimeter. The main experiment was the proppant pack tests conducted in the glass column at ambient conditions in which coal slurry flowed into a proppant treated with SNPs. This was compared with proppant without any SNP treatment. The results of the coal slurry were obtained using a particle counter analyzer. The corresponding experimental workflow is shown in Figure 2.

### **3. Results and Discussion**

#### **3.1. Silica Nanoparticles dispersion using SDBS**

In order to modify the dispersion stability and surface chemistry of SNPs, an anionic surfactant SDBS was used. In the three dispersion mediums (DI water, 0.01 M NaCl, and 0.6 M NaCl) tested, SDBS reduced the zeta-potential and effectively enhanced the dispersion stability, as shown in Figure 3. Note that the dispersion stability is more effective in DI water and low salinity (0.01 M NaCl) rather than in the high salinity (0.6 M NaCl) suspension.

The zeta-potential measurements of bare SNPs in both ionic strengths are consistent with Al-Anssari et al. (2017) (Al-Anssari et al. 2017a). With increases in ionic strength, the absolute zeta-potential value decreases, resulting in reduced dispersion stability. However, the DI water and low ionic strength (0.01 M NaCl brine) provide better stability enhancement when SNPs are treated with SDBS.

#### **3.2. Effect of Nanoparticles adhesion onto proppant pack**

In order to examine the coating of nanoparticles via the soaking method, we first calibrated SNPs in DI water. The SNPs turbidity increases with an increase in SNP loading, as can be seen in Figure 4. Note that the turbidimeter has a limitation of 1000 NTUs. When on the x-axis, SNP loading is increased while on the y-axis, the turbidity value in NTU increased with the loading resulting in a slope value of 3390.5.



It was observed that higher salinity has lower zeta-potential, which leads to higher retention efficiency of SNPs by soaking method, as seen in Figure 5. The results show that SNPs based in DI water yielded retention efficiency of 61-67%, while 0.01 M NaCl (as comparable to potable water) yielded 60-72% retention efficiency, and 0.6 M NaCl (as comparable to seawater) yielded 81-85% retention of SNPs onto the glass bead proppant pack. This retention is due to the zeta-potential values, as obtained in Section 3.1, which can also be seen in Figure 3. Thus, aggregation of nanoparticles in 0.6 M NaCl ionic strength due to its low zeta-potential, aids it in retaining SNPs in the proppant pack.

Thus, in further experiments after observing better retention of 0.6 M NaCl cases in two coal concentrations (0.01 wt% and 0.1 wt%), we conducted the rest of the experiments of adsorption in 0.6 M NaCl salinity. This is consistent with the DLVO theory, which defines principles based on which the particles (in our case SNPs) aggregation take place at higher salinities.

### 3.3. Effect of Chemically modified Nanoparticles on coal fines fixation

Chemically modified nanoparticles (in this case, silica nanoparticles treated with SDBS) were injected into the glass-column, followed by the introduction of the glass-bead proppant pack. The results showed that 0.1 wt% of SNPs yielded maximum adsorption of all tested coal fines (0.1, 0.5, and 1 wt%), as can be seen in Figure 6. Note that there is a difference in adsorption of coal fines with weight percentages (even when passing through an untreated proppant pack), as a higher concentration of slurry yields lower dispersion stability, leading to clogging in the proppant pack (Al-Anssari *et al.* 2017a).

The base case has been optimized in our previous work (Awan *et al.* 2019), giving a  $C_{\text{eff}}/C_o$  of approximately 83%, meaning the adsorption of coal fines is 17% (using 0.1 wt% coal fines treated with 0.001 wt% SDBS). The rest of the coal slurries also have 0.001 wt% SDBS, but their coal fines are of higher weight fraction. It can also be observed that untreated proppant packs in various coal concentrations result in an increasing trend to rising coal concentration, i.e., 17% adsorption for 0.1 wt% coal fines, 27% adsorption for 0.5 wt% coal fines, and 30% adsorption for 1.0 wt% coal fines. This occurs due to the lower stability of the coal slurry as a result of the increase in weight (Al-Anssari *et al.* 2017a), which ultimately causes the straining of coal fines due to their aggregation. Additionally, not all of the coal fines retention in the proppant pack is due to the interaction of attractive forces of nanoparticles with coal fines, there

is also an aggregation of coal fines and straining in the proppant pack as has been demonstrated by Zou et al. (2014) (Zou *et al.* 2014) which can be seen in Fig. 6.

With increasing the SNP loading in the proppant pack, its retention efficiency also increases. Thus, the nanoparticle treated glass beads can retard the mobilization of coal fines through the proppant pack and affix them near the source of their generation; thereby, reducing the damage to the pumps and minimizing the possibility of filling of the wellbore.

#### **4. Conclusion**

The above sets of experiments conclude that higher salinity yields higher coating efficiency of the proppant pack via nanoparticles due to their aggregation behavior (zeta-potential values of greater than -20 mV). SDBS enhances the dispersion stability of silica nanoparticles in various salinities tested up to 0.6 M NaCl. An optimum concentration of 0.1 wt% SNPs yielded maximum adsorption of coal fines in the proppant pack at higher ionic strength (0.6 M NaCl brine).

Further studies involving a comparison of various coating methods (e.g., calcination, sintering, soaking, oil coating, etc.) for irreversibly affixing nanoparticles on the proppant pack need to be conducted, in order to optimize the coating procedure in various saline environments. Further, coal particles of different ranks need to be studied to understand the behavior of various metal oxide nanoparticles, in order to fixate these coal fines by adsorption in the proppant pack. A comprehensive study to determine the impact of adsorption on the permeability can also be studied, as its implication in the field can be detrimental to natural gas recovery.

#### **Conflicts of Interest**

None.

#### **Acknowledgments**

This work was supported by the Higher Education Commission (HEC) Pakistan vide approval letter No. 5-1/HRD/UESTPI(Batch-V)/3371/2017/HEC) and Edith Cowan University (ECU) Australia Early Career Research Grant G1003450. The authors would like to thank HEC, Pakistan, and ECU, Australia, for the Ph.D. grant vide ECU-HEC Joint Scholarship-2017.

## References

- Abhishek, R., and Hamouda, A. (2017). Effect of Various Silica Nanofluids: Reduction of Fines Migrations and Surface Modification of Berea Sandstone. *Applied Sciences* **7**(12).
- Ahmadi, M., Habibi, A., Pourafshary, P., and Ayatollahi, S. (2013a). An Experimental Study of Interaction between Nanoparticles' Deposition on a Sintered Porous Medium and Migratory Fines. *Journal of Porous Media* **16**(5), 459-467.
- Ahmadi, M., Habibi, A., Pourafshary, P., and Ayatollahi, S. (2013b). Zeta-Potential Investigation and Experimental Study of Nanoparticles Deposited on Rock Surface to Reduce Fines Migration. (June 2013), 534-544.
- Al-Anssari, S., Arif, M., Wang, S., Barifcani, A., and Iglauer, S. (2017a). Stabilising Nanofluids in Saline Environments. *Journal of Colloid and Interface Science* **508**, 222-229.
- Al-Anssari, S., Barifcani, A., Keshavarz, A., and Iglauer, S. (2018). Impact of Nanoparticles on the Co<sub>2</sub>-Brine Interfacial Tension at High Pressure and Temperature. *Journal of Colloid and Interface Science* **532**, 136-142.
- Al-Anssari, S., Barifcani, A., Wang, S., Maxim, L., and Iglauer, S. (2016). Wettability Alteration of Oil-Wet Carbonate by Silica Nanofluid. *Journal of Colloid and Interface Science* **461**, 435-442.
- Al-Anssari, S., Nwidee, L. N., Ali, M., Sangwai, J. S., Wang, S., Barifcani, A., and Iglauer, S. (2017b). Retention of Silica Nanoparticles in Limestone Porous Media. In 'SPE/IATMI Asia Pacific Oil & Gas Conference and Exhibition'. (Society of Petroleum Engineers: Jakarta, Indonesia.)
- Arab, D., Pourafshary, P., Ayatollahi, S., and Habibi, A. (2014). Remediation of Colloid-Facilitated Contaminant Transport in Saturated Porous Media Treated by Nanoparticles. *International Journal of Environmental Science and Technology* **11**(1), 207-216.
- Asl, H. F., Zargar, G., Manshad, A. K., Takassi, M. A., Ali, J. A., and Keshavarz, A. (2020). Effect of SiO<sub>2</sub> Nanoparticles on the Performance of L-Arg and L-Cys Surfactants for Enhanced Oil Recovery in Carbonate Porous Media. *Journal of Molecular Liquids* **300**, 112290.
- Assef, Y., Arab, D., and Pourafshary, P. (2014). Application of Nanofluid to Control Fines Migration to Improve the Performance of Low Salinity Water Flooding and Alkaline Flooding. *Journal of Petroleum Science and Engineering* **124**, 331-340.
- Awan, F. U. R., Keshavarz, A., Akhondzadeh, H., Nosrati, A., Al-Anssari, S., and Iglauer, S. (2019). Optimizing the Dispersion of Coal Fines Using Sodium Dodecyl Benzene Sulfonate. In 'SPE/AAPG/SEG Asia Pacific Unconventional Resources Technology Conference'. pp. 9.(Unconventional Resources Technology Conference: Brisbane, Australia.)
- Badalyan, A., Beasley, T., Nguyen, D., Keshavarz, A., Schacht, U., Carageorgos, T., You, Z., Bedrikovetsky, P., Hurter, S., and Troth, I. (2016). Laboratory and Mathematical Modelling of

- Fines Production from Csg Interburden Rocks. In 'SPE Asia Pacific Oil & Gas Conference and Exhibition'. pp. 30.(Society of Petroleum Engineers: Perth, Australia.)
- Bahraminejad, H., Khaksar Manshad, A., Riazi, M., Ali, J. A., Sajadi, S. M., and Keshavarz, A. (2019). CuO/TiO<sub>2</sub>/Pam as a Novel Introduced Hybrid Agent for Water—Oil Interfacial Tension and Wettability Optimization in Chemical Enhanced Oil Recovery. *Energy & Fuels* **33**(11), 10547-10560.
- Bai, T., Chen, Z., Aminossadati, S. M., Pan, Z., Liu, J., and Li, L. (2015). Characterization of Coal Fines Generation: A Micro-Scale Investigation. *Journal of Natural Gas Science and Engineering* **27**, 862-875.
- Bai, T., Chen, Z., Aminossadati, S. M., Rufford, T. E., and Li, L. (2017). Experimental Investigation on the Impact of Coal Fines Generation and Migration on Coal Permeability. *Journal of Petroleum Science and Engineering* **159**, 257-266.
- Belcher, C. K., Seth, K., Hollier, R., and Paternostro, B. P. (2010). Maximizing Production Life with the Use of Nanotechnology to Prevent Fines Migration. In 'International Oil and Gas Conference and Exhibition in China'. (Society of Petroleum Engineers: Beijing, China.)
- Bera, A., and Belhaj, H. (2016). Application of Nanotechnology by Means of Nanoparticles and Nanodispersions in Oil Recovery - a Comprehensive Review. *Journal of Natural Gas Science and Engineering* **34**, 1284-1309.
- Bin, Y., Moghanloo, R. G., and Zheng, D. (2016). Analytical Evaluation of Nanoparticle Application to Mitigate Fines Migration in Porous Media. *Spe Journal* **21**(6), 2317-2332.
- Blume, T., Weisbrod, N., and Selker, J. S. (2005). On the Critical Salt Concentrations for Particle Detachment in Homogeneous Sand and Heterogeneous Hanford Sediments. *Geoderma* **124**(1), 121-132.
- Elena Rodríguez, S. L. B. Trapping of Fine Particles in Gaps in Porous Media. In 'International Symposium of the Society of Core Analysts', 10-12 September, 2007 2007, Calgary, Canada,
- Geng, Y., Tang, D., Xu, H., Tao, S., Tang, S., Ma, L., and Zhu, X. (2017). Experimental Study on Permeability Stress Sensitivity of Reconstituted Granular Coal with Different Lithotypes. *Fuel* **202**, 12-22.
- Guo, Z., Hussain, F., and Cinar, Y. (2015). Permeability Variation Associated with Fines Production from Anthracite Coal During Water Injection. *International Journal of Coal Geology* **147-148**, 46-57.
- Guo, Z. H., Hussain, F., and Cinar, Y. (2016). Physical and Analytical Modelling of Permeability Damage in Bituminous Coal Caused by Fines Migration During Water Production. *Journal of Natural Gas Science and Engineering* **35**, 331-346.
- Habibi, A., Ahmadi, M., Pourafshary, P., and Ayatollahi, S. (2014). Fines Migration Control in Sandstone Formation by Improving Silica Surface Zeta Potential Using a Nanoparticle Coating Process. *Energy Sources Part a-Recovery Utilization and Environmental Effects* **36**(21), 2376-2382.

- Habibi, A., Ahmadi, M., Pourafshary, P., Ayatollahi, S., and Al-Wahaibi, Y. (2013). Reduction of Fines Migration by Nanofluids Injection: An Experimental Study. *SPE Journal*(April 2013), 309-318.
- Han, G., Ling, K., Wu, H., Gao, F., Zhu, F., and Zhang, M. (2015). An Experimental Study of Coal-Fines Migration in Coalbed-Methane Production Wells. *Journal of Natural Gas Science and Engineering* **26**, 1542-1548.
- Hasannejada, R., Pourafshary, P., Vatani, A., and Sameni, A. (2017). Application of Silica Nanofluid to Control Initiation of Fines Migration. *Petroleum Exploration and Development* **44**(5), 850-859.
- Huang, T., Crews, J. B., Gabrysch, A. D., and Jeffrey, R. M. (2010a). Controlling Coal Fines in Coal Bed Operations. In 'United States Patent Application Publication'. pp. 10.(Baker Hughes Incorporated, Houston, TX (US): United States.)
- Huang, T., Crews, J. B., and Willingham, J. R. (2008a). Nanoparticles for Formation Fines Fixation and Improving Performance of Surfactant Structure Fluids. In 'International Petroleum Technology Conference'. (International Petroleum Technology Conference: Kuala Lumpur, Malaysia.)
- Huang, T., Crews, J. B., and Willingham, J. R. (2008b). Using Nanoparticle Technology to Control Fine Migration. In 'SPE Annual Technical Conference and Exhibition'. (Society of Petroleum Engineers: Denver, Colorado, USA.)
- Huang, T., Evans, B. A., Crews, J. B., and Belcher, C. K. (2010b). Field Case Study on Formation Fines Control with Nanoparticles in Offshore Applications. In 'SPE Annual Technical Conference and Exhibition'. (Society of Petroleum Engineers: Florence, Italy.)
- Keshavarz, A., Badalyan, A., Carageorgos, T., Bedrikovetsky, P., and Johnson, R. (2015). Stimulation of Coal Seam Permeability by Micro-Sized Graded Proppant Placement Using Selective Fluid Properties. *Fuel* **144**, 228-236.
- Keshavarz, A., Badalyan, A., Johnson, R., and Bedrikovetsky, P. (2016). Productivity Enhancement by Stimulation of Natural Fractures around a Hydraulic Fracture Using Micro-Sized Proppant Placement. *Journal of Natural Gas Science and Engineering* **33**, 1010-1024.
- Keshavarz, A., Yang, Y., Badalyan, A., Johnson, R., and Bedrikovetsky, P. (2014). Laboratory-Based Mathematical Modelling of Graded Proppant Injection in Cbm Reservoirs. *International Journal of Coal Geology* **136**, 1-16.
- Khilar, K. C., and Fogler, H. S. (1984). The Existence of a Critical Salt Concentration for Particle Release. *Journal of Colloid and Interface Science* **101**(1), 214-224.
- Kia, S. F., Fogler, H. S., and Reed, M. G. (1987). Effect of Ph on Colloidally Induced Fines Migration. *Journal of Colloid and Interface Science* **118**(1), 158-168.
- Kumar, A., Yadav, N., Rao, Y. R. L., Singhal, C. P., and Kumar, A. (2012). Pre-Fracture Treatment of Coal Seams for Fracture Conductivity Enhancement in Hydro Fracturing of Cbm

- Wells and Coal Fines Mitigation in Multilateral Cbm Wells through Wettability Alteration of Coal Fines - a Laboratory Study. In 'SPE Oil and Gas India Conference and Exhibition'. pp. 9.(Society of Petroleum Engineers: Mumbai, India.)
- Lever, A., and Dawe, R. A. (1984). Water-Sensitivity and Migration of Fines in the Hopeman Sandstone. *Journal of Petroleum Geology* **7**(1), 97-107.
- Liang, F., Sayed, M., Al-Muntasheri, G. A., Chang, F. F., and Li, L. (2016). A Comprehensive Review on Proppant Technologies. *Petroleum* **2**(1), 26-39.
- Magill, D. P., Ramurthy, M., Jordan, R., and Nguyen, P. D. (2010). Controlling Coal-Fines Production in Massively Cavitated Openhole Coalbed-Methane Wells. In 'SPE Asia Pacific Oil and Gas Conference and Exhibition'. (Society of Petroleum Engineers: Brisbane, Queensland, Australia.)
- Mahdi Jafari, S., He, Y., and Bhandari, B. (2006). Nano-Emulsion Production by Sonication and Microfluidization—a Comparison. *International Journal of Food Properties* **9**(3), 475-485.
- Marcinew, R. P., and Hinkel, J. J. (1990). Coal Fines-Origin, Effects and Methods to Control Associated Damage. In 'Annual Technical Meeting'. (Petroleum Society of Canada: Calgary, Alberta.)
- Mohan, K. K., and Fogler, H. S. (1997). Colloidally Induced Smectitic Fines Migration: Existence of Microquakes. *Aiche Journal* **43**(3), 565-576.
- Moore, T. A. (2012). Coalbed Methane: A Review. *International Journal of Coal Geology* **101**, 36-81.
- Najimi, S., Nowrouzi, I., Manshad, A. K., Farsangi, M. H., Hezave, A. Z., Ali, J. A., Keshavarz, A., and Mohammadi, A. H. (2019). Investigating the Effect of [C8py][Cl] and [C18py][Cl] Ionic Liquids on the Water/Oil Interfacial Tension by Considering Taguchi Method. *Journal of Petroleum Exploration and Production Technology* **9**(4), 2933-2941.
- Palmer, I. D., Moschovidis, Z. A., and Cameron, J. R. (2005). Coal Failure and Consequences for Coalbed Methane Wells. In 'SPE Annual Technical Conference and Exhibition'. pp. 11.(Society of Petroleum Engineers: Dallas, Texas.)
- Pan, L.-h., Zhang, S.-c., Zhang, J., and Lin, X. (2015). An Experimental Study on Screening of Dispersants for the Coalbed Methane Stimulation. *International Journal of Oil, Gas and Coal Technology* **9**(4), 437-454.
- Parker, M. A., Ramurthy, K., and Sanchez, P. W. (2012). New Proppant for Hydraulic Fracturing Improves Well Performance and Decreases Environmental Impact of Hydraulic Fracturing Operations. In 'SPE Eastern Regional Meeting'. pp. 10.(Society of Petroleum Engineers: Lexington, Kentucky, USA.)
- Patel, A., Goh, C., Towler, B. R., Victor, and Rufford, T. E. (2016). Screening of Nanoparticles to Control Clay Swelling in Coal Bed Methane Wells. In 'International Petroleum Technology Conference'. (International Petroleum Technology Conference: Bangkok, Thailand.)

- Qajar, J., Francois, N., and Arns, C. H. (2013). Microtomographic Characterization of Dissolution-Induced Local Porosity Changes Including Fines Migration in Carbonate Rock. *Spe Journal* **18**(3), 545-562.
- Rosenbrand, E., Kjølner, C., Riis, J. F., Kets, F., and Fabricius, I. L. (2015). Different Effects of Temperature and Salinity on Permeability Reduction by Fines Migration in Berea Sandstone. *Geothermics* **53**, 225-235.
- Rozo, R. E., Paez, J., Mendoza Rojas, A., Milne, A. W., Soler, D. F., and Abuseif, H. (2007). An Alternative Solution to Sandstone Acidizing Using a Nonacid Based Fluid System with Fines-Migration Control. In 'SPE Annual Technical Conference and Exhibition'. (Society of Petroleum Engineers: Anaheim, California, U.S.A.)
- Schembre, J. M., and Kovscek, A. R. (2005). Mechanism of Formation Damage at Elevated Temperature. *Journal of Energy Resources Technology* **127**(3), 171-180.
- Sharma, M. M., Chamoun, H., Sarma, D. S. H. S. R., and Schechter, R. S. (1992). Factors Controlling the Hydrodynamic Detachment of Particles from Surfaces. *Journal of Colloid and Interface Science* **149**(1), 121-134.
- Shen, M., and Resasco, D. E. (2009). Emulsions Stabilized by Carbon Nanotube–Silica Nanohybrids. *Langmuir* **25**(18), 10843-10851.
- Shi, Q., Qin, Y., Zhou, B., Zhang, M., Wu, M., and Wang, L. (2018). An Experimental Study of the Agglomeration of Coal Fines in Suspensions: Inspiration for Controlling Fines in Coal Reservoirs. *Fuel* **211**, 110-120.
- Yang, J., Ji, S., Li, R., Qin, W., and Lu, Y. (2015). Advances of Nanotechnologies in Oil and Gas Industries. *Energy Exploration & Exploitation* **33**(5), 639-657.
- Yousefvand, H., and Jafari, A. (2015). Enhanced Oil Recovery Using Polymer/Nanosilica. *Procedia Materials Science* **11**, 565-570.
- Yuan, B. (2017). Modeling Nanofluid Utilization to Control Fines Migration. University of Oklahoma, Norman, Oklahoma.
- Yuan, B., and Moghanloo, R. G. (2018). Nanofluid Pre-Treatment, an Effective Strategy to Improve the Performance of Low-Salinity Waterflooding. *Journal of Petroleum Science and Engineering* **165**, 978-991.
- Yuan, B., and Wood, D. (2018). A Comprehensive Review of Formation Damage During Enhanced Oil and Gas Recovery. *Journal of Petroleum Science and Engineering*.
- Zeinijahromi, A., Vaz, A., Bedrikovetsky, P., and Borazjang, S. (2012). Effects of Fines Migration on Well Productivity During Steady State Production. *Journal of Porous Media* **15**(7), 665-679.

- 510 Zhao, X., Liu, S., Sang, S., Pan, Z., Zhao, W., Yang, Y., Hu, Q., and Yang, Y. (2016).  
511 Characteristics and Generation Mechanisms of Coal Fines in Coalbed Methane Wells in the  
512 Southern Qinshui Basin, China. *Journal of Natural Gas Science and Engineering* **34**, 849-863.  
513
- 514 Zheng, X., Perreault, F., and Jang, J. (2018). Fines Adsorption on Nanoparticle-Coated Surface.  
515 *Acta Geotechnica* **13**(1), 219-226.  
516
- 517 Zou, Y. S., Zhang, S. C., and Zhang, J. (2014). Experimental Method to Simulate Coal Fines  
518 Migration and Coal Fines Aggregation Prevention in the Hydraulic Fracture. *Transport in*  
519 *Porous Media* **101**(1), 17-34.  
520



521

## Biographies

522 Faisal Ur Rahman Awan is a Ph.D. candidate in Petroleum Engineering  
523 at Edith Cowan University, Australia. His work focuses specifically on  
524 the coal fines fixation using nanoparticles. Mr. Awan did his Bachelor's  
525 and Master's degrees in Petroleum Engineering. He has also been serving  
526 at Dawood University of Engineering and Technology, Karachi, as an  
527 Assistant Professor in Petroleum Engineering for the last seven years. He  
528 is a member of prestigious societies such as SPE, SEG, EI, and PEC.



529

530

531 Alireza holds a Ph.D. degree in Petroleum Engineering from the  
532 University of Adelaide, an M.Sc. degree in Reservoir Engineering from  
533 the University of Tehran (Iran), and a B.Sc. degree in Chemical-Petroleum  
534 Engineering from Petroleum University of Technology (Iran). He is  
535 presently serving as a Senior Lecturer at the School of Engineering at  
536 Edith Cowan University. Before joining ECU, Alireza was a research  
537 scientist in the CSIRO-Energy business unit, where he researched  
538 enhancing gas production from unconventional resources and CO<sub>2</sub>-  
539 sequestration. Before pursuing his Ph.D. study, he was a Petroleum  
540 Engineer in the National Iranian Oil Company (NIOC) for six years.  
541 Alireza's research interests focus on Enhanced Oil/Gas Recovery from  
542 conventional and unconventional reservoirs. He is a member of SPE.



543

544 Hamed completed his Bachelor's and Master's in Petroleum Engineering.  
545 During his Master's study, he conducted numerical research on heavy oil  
546 EOR. He used two of the most professional petroleum simulators, CMG  
547 and Eclipse, in his studies. He changed his research field to Coalbed  
548 Methane in 2016 and received a scholarship for his Ph.D. studies at Edith  
549 Cowan University (ECU), Australia. For the time being, as a Ph.D. student  
550 at ECU, he is experimentally researching on Coalbed Methane productivity  
551 enhancement as his priority, and also partially on enhanced oil recovery and  
552 CO<sub>2</sub> geo-sequestration. He is a member of SPE.



553

554 Sarmad Al-Anssari is currently a senior lecturer in Chemical Engineering at  
555 University of Baghdad, Iraq. He earned a bachelor's and master's degree in  
556 chemical engineering from University of Baghdad and he holds a PhD  
557 degree in chemical engineering/ Nanotechnology from Curtin University/  
558 Australia. He worked as a faculty member in the university of Baghdad for  
559 more than 10 years and recently he is adjunct lecturer at ECU Australia and  
560 external supervisor at Curtin university/ Australia. His research interest is  
561 on different applications of nanoparticles and nanofluids in different  
562 disciplines, including wettability alteration, enhanced oil recovery, and  
563 carbon capture and storage.



564

565

566

567

568 Stefan Iglauer joined Edith Cowan University (ECU) in 2018 as a Professor  
569 to lead the developments in the Petroleum Engineering discipline. His  
570 research interests are in petrophysics and interfacial phenomena, mainly at  
571 pore-scale with a focus on CO<sub>2</sub> geo-sequestration and improved  
572 hydrocarbon recovery. Stefan has authored more than 250 technical  
573 publications; he holds a Ph.D. degree in material science from Oxford  
574 Brookes University (UK) and an MSc degree from the University of  
575 Paderborn (Germany). He is a member of SPE.



576  
577

Table 1: Properties of coal sample

Ash (%, db <sup>a</sup> )	Density (g/cm <sup>3</sup> )	Volatile matter (%, daf <sup>a</sup> )	C (%, daf <sup>a</sup> )	H (%, daf <sup>a</sup> )	R <sub>v</sub> , max <sup>a</sup> (%)	Vitrinite (vol% mmf <sup>a</sup> )	Inertinite (vol% mmf <sup>a</sup> )	Liptinite (vol% mmf <sup>a</sup> )
4.798	1.31	5.042	78.50	5.37	0.91	81.01	12.73	6.26

<sup>a</sup> **db**: on a dry basis; **daf**: dried ash-free; **R<sub>v</sub>, max**: maximum vitrinite reflectance; **mmf**: mineral matter free.


578  
579  
580  
581

Table 2: Properties of glass beads used as proppant packs

Chemical	SiO <sub>2</sub>	Na <sub>2</sub> O	CaO	MgO	Al <sub>2</sub> O <sub>3</sub>	FeO/Fe <sub>2</sub> O <sub>3</sub>	Trace
Wt %	72.5	13.6	9.7	3.4	0.4	0.2	0.2


582  
583

Table 3: Characteristics of nanoparticles

Nanoparticle	Linear Formula	Primary particle size (nm)	Chemical Structure Depiction	Specific surface area (m <sup>2</sup> /g)	Purity (%)	Density (g/cc)	Molecular mass (g/mol) @ 298.15 K	Boiling point (K)	Melting point (K)	Additional Description
Silicon dioxide	SiO <sub>2</sub>	5-15		140	≥ 99.50	2.20- 2.60	60.08	2503	1873	Porous spherical

584

585

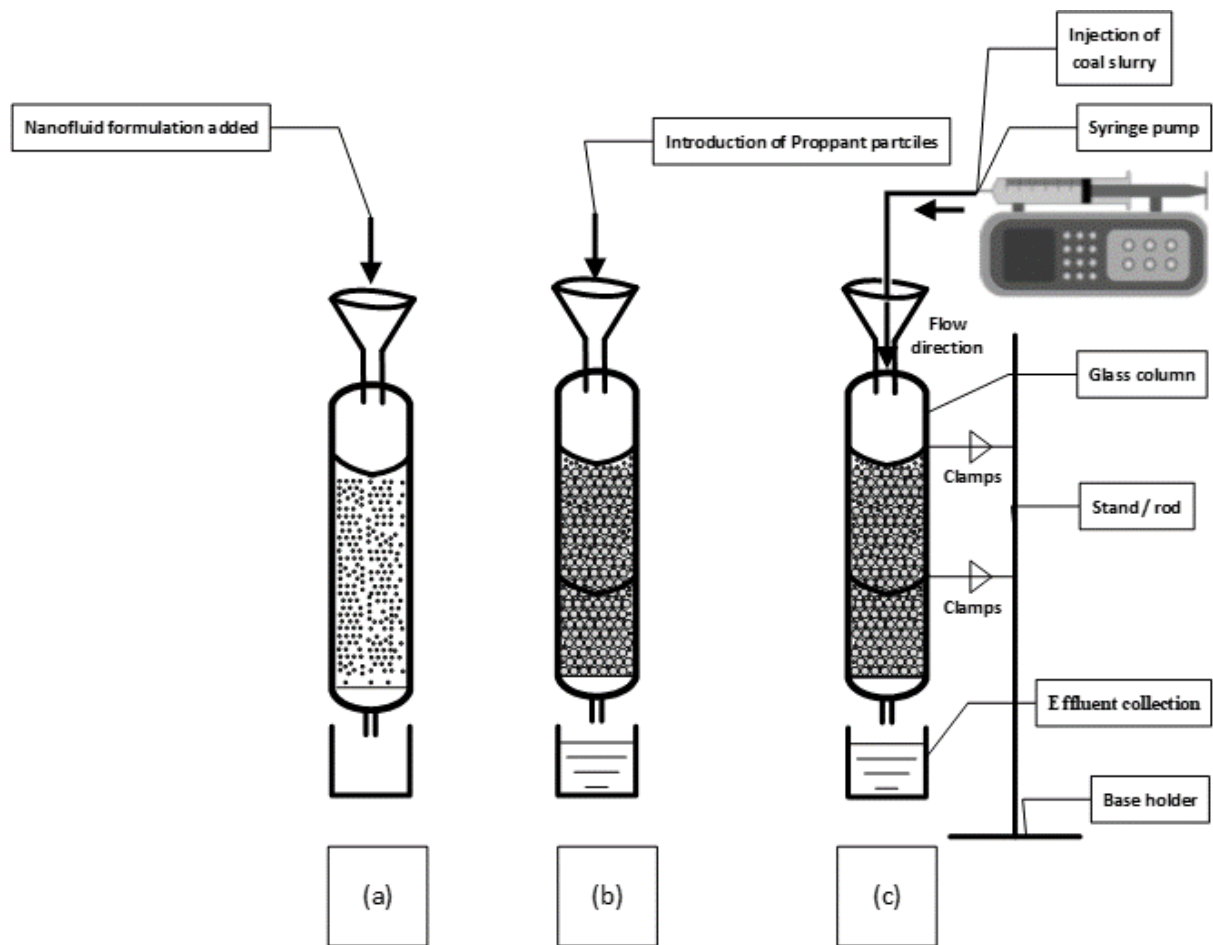

586

587

588

589

Figure 1: Schematic of (a) Silica nano-formulation added to the glass column, (b) Introduction of proppant particles in the nano-formulation (c) Injection of coal slurry at 1 mL/min

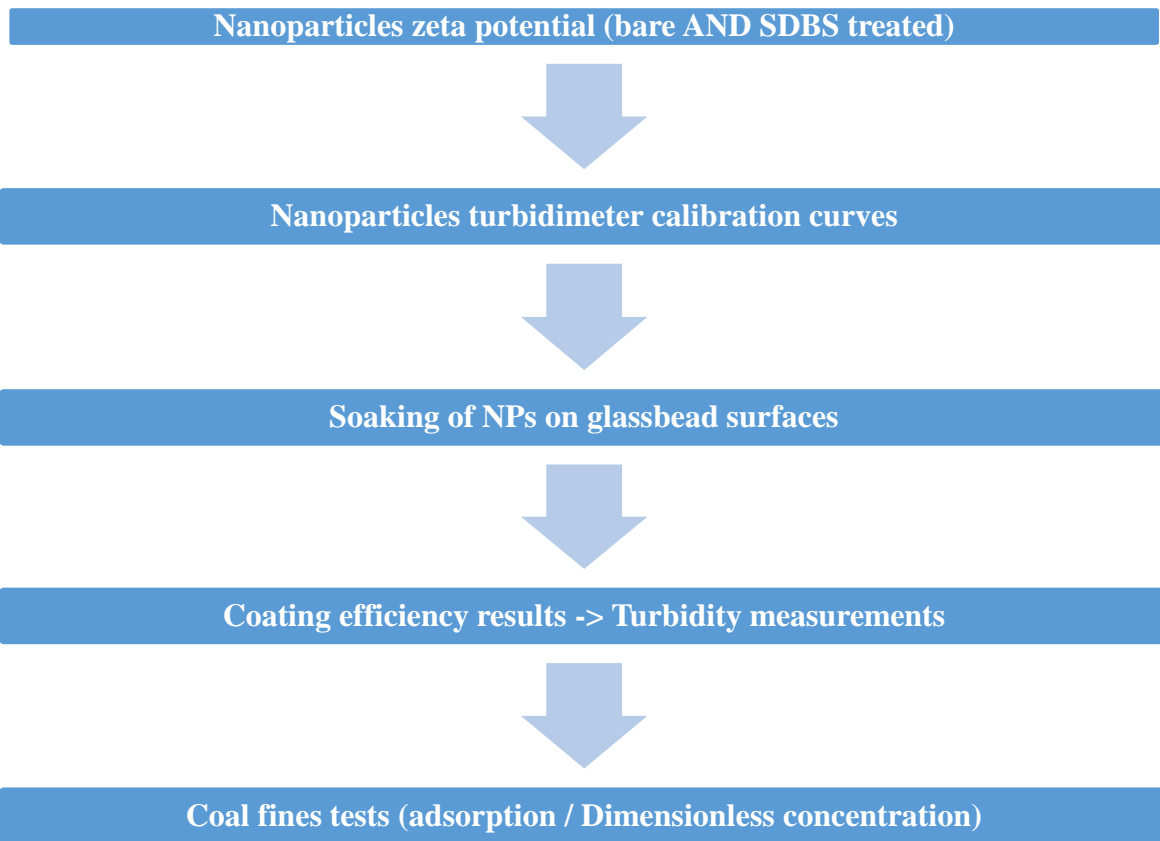


Figure 2: Workflow of experiments for determining the effect of nanoparticles on adsorption of coal fines

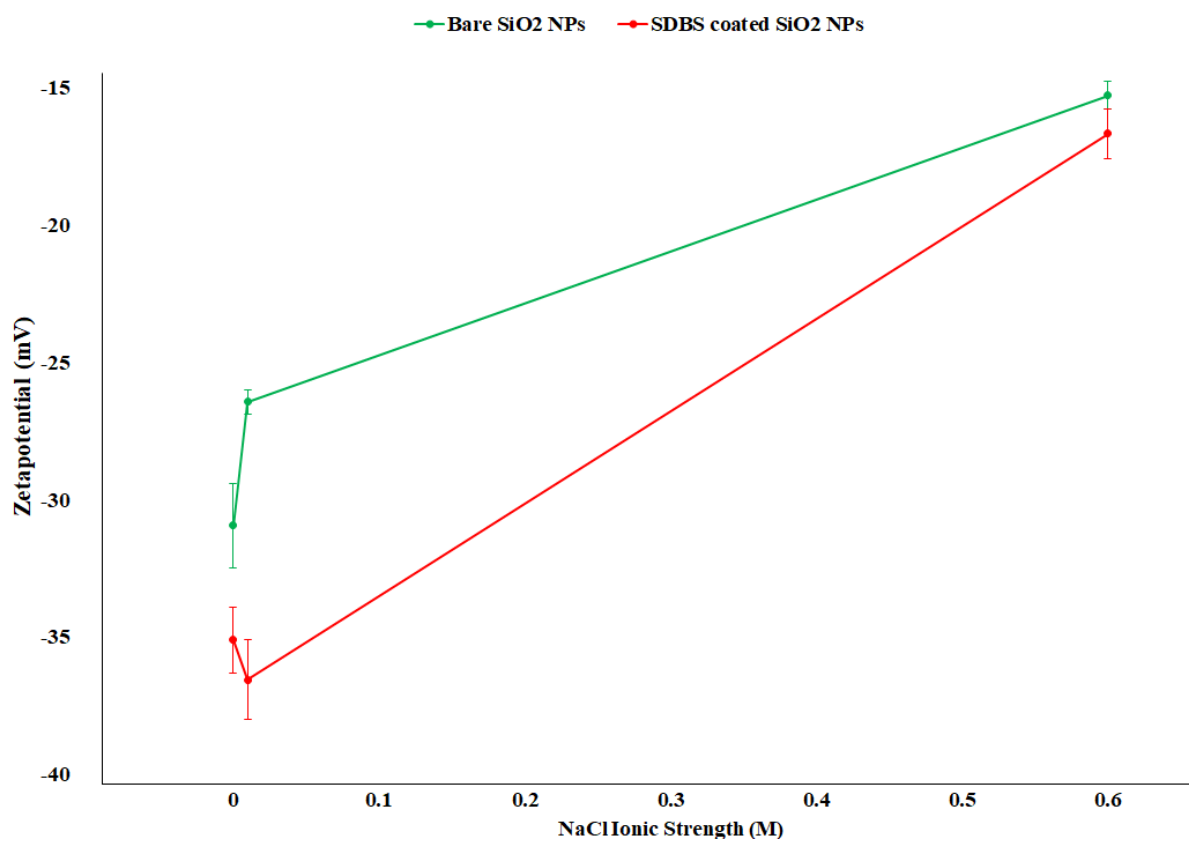


Figure 3: Effect of SDBS in various ionic strength (0, 0.01 and 0.6 M NaCl brines) on zeta-potential for 0.1 wt% silica NPs at pH=9 and temperature=298.15 K.

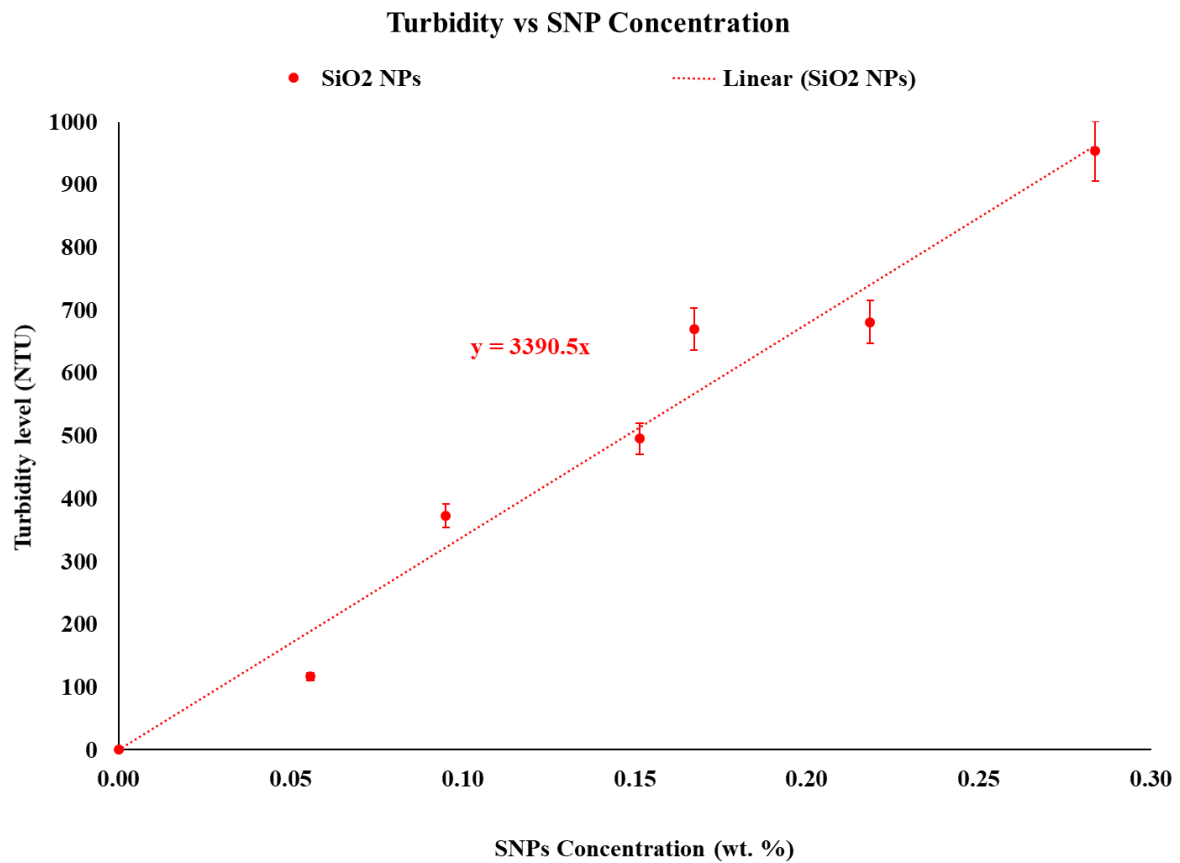


Figure 4: Turbidity results of silica nanoparticles in various concentrations from 0 to 0.3 wt%  
( $R^2$  of the Linear SiO<sub>2</sub> is 0.967)

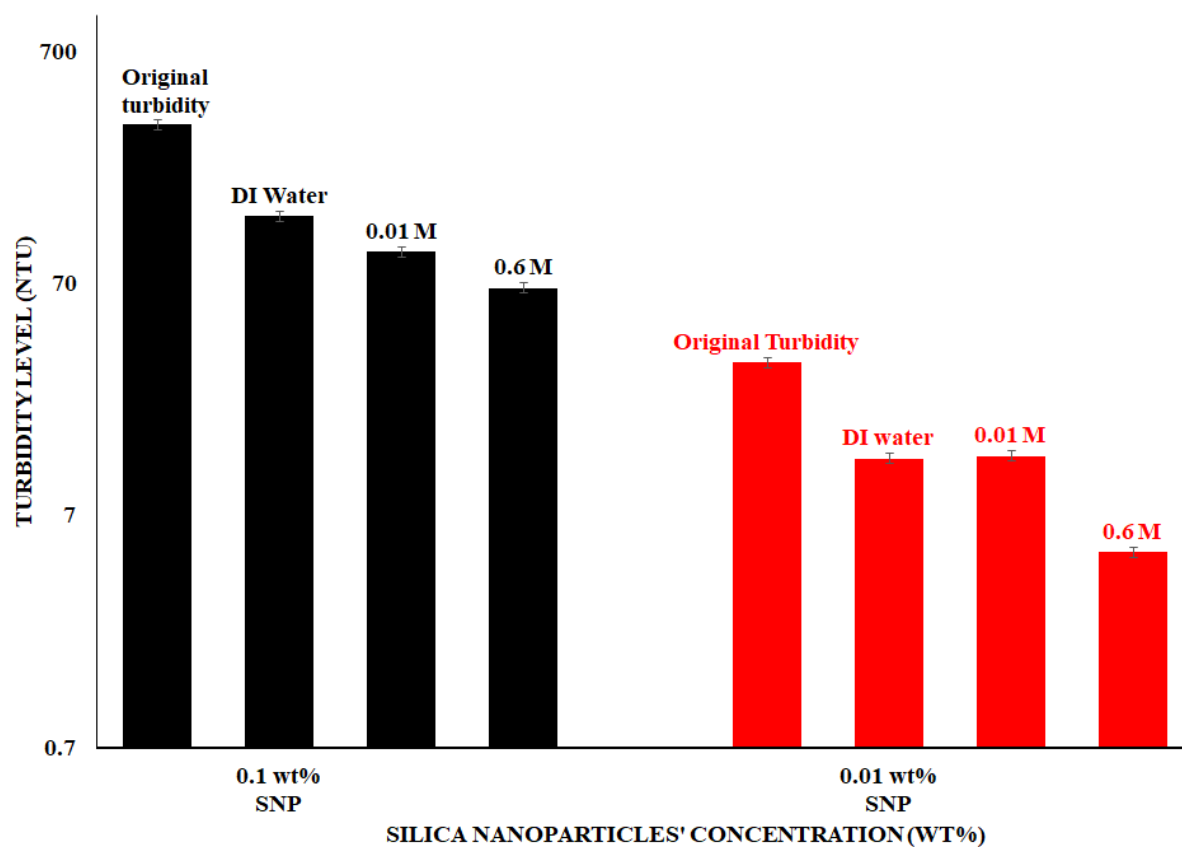


Figure 5: Turbidity results for silica nanoparticles coating via soaking method results in various suspensions (DI water, 0.01 M, and 0.6 M NaCl brines)



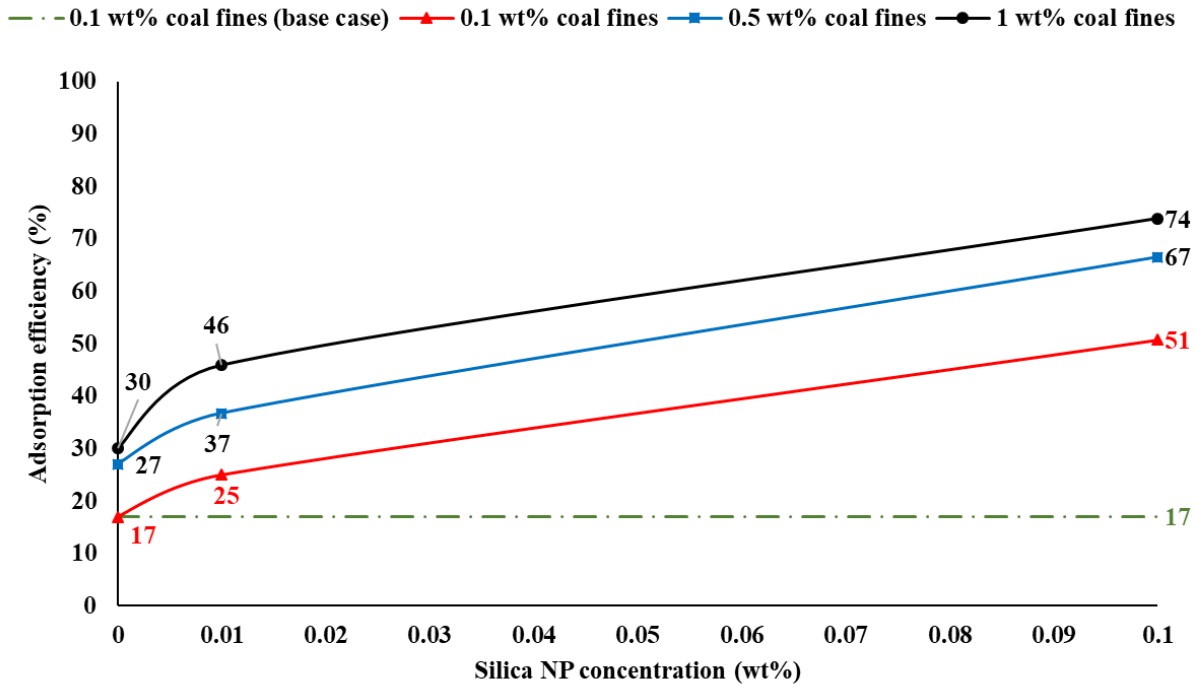


Figure 6: Results of adsorption of the various coal fines concentrations (0.1, 0.5, and 1 wt%) using no nanoparticles, 0.01 wt%, and 0.1 wt% in 0.6 M saline environment in a proppant pack. Note the base case is 0.1 wt% coal fines passed through the untreated proppant pack